

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106


1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400

TEST REPORT

Client : Milliken (Australia) Pty Ltd 171 Briens Road Northmead NSW 2152

Test Number	:	23-002678	
Issue Date	:	24/08/2023	
Print Date	:	24/08/2023	
Order Number	r :	6701491012	

Sample Description	Clients Ref :	"Cool Stripe Base (Multi-Colour/Multi-Design)
	Loop pile carpe	t tile with WellBac comfort (PVC free) backing
	End Use : Flo	ooring
	Nominal Compo	osition : 100% Nylon

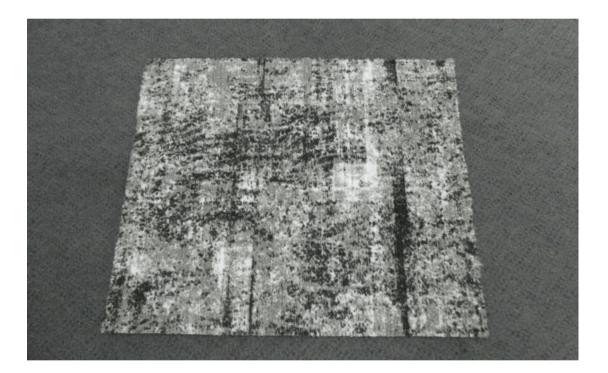

302946

65487

C Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

Chris Campbell

Chris Campbell APPROVED SIGNATORY



Page 1 of 3



ICHAEL A. JACKSON B.Sc.(Hons)



Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400

		TEST	REPORT				
Client :	Milliken (Au	ustralia) Pty Ltd		Test I	Number :	23-00267	8
	171 Briens	Road		Issue	Date :	24/08/202	23
Northmead NSW 2152			Print	Date :	24/08/202	23	
			Order Number :			6701491012	
O 9239.1:20	010 Part 1	Reaction to Fire Tests for Floor Radiant Heat Source	ings. Determinati	on of the Bur	ning Behavi	our using a	
		Date of Sample Arrival		10-07-	-2023		
		Date Tested		24-08-	-2023		
		CHF Value	1	2	3	Mean	
		Length	6.3	-	-	-	kW/m²
		Width	6.1	6.3	6.3	6.2	kW/m²
		HF-30 Value	1	2	3	Mean	
		Width	6.1	-	-	-	kW/m²
		Smoke Value	1	2	3	Mean	
		Length	177	-	-	-	%.min
		Width	139	182	205	175	%.min

302946

65487

C Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

1.

Chris Campbell



Page 2 of 3



MICHAEL A. JACKSON B.Sc.(Hons)



Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400

TEST REPORT

Client :	Milliken (Australia) Pty Ltd	
	171 Briens Road	
	Northmead NSW 2152	

Test Number	:	23-002678
Issue Date	:	24/08/2023
Print Date	:	24/08/2023
Order Number	:	6701491012

Observation Melting

Yes

The test results relate to the behaviour of the test specimens of a product under the particular conditions of the test, they are not intended to be sole criterion for assessing the potential fire hazard of the product in use.

Sample was conditioned in accordance with BSEN 13238:2010 at a temperature of 23±2°C and relative humidity of 50±5% for a minimum of 48 hours prior to testing.

Results in accordance with section 9.4 have not been included in the report. They are available upon request.

Each specimen was adhered to a substrate of 6mm thick fibre reinforced cement board using Roberts 656 adhesive and clamped prior to testing.

302946

65487

C Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

Chris Campbell





Page 3 of 3

IICHAEL A. JACKSON B.Sc.(Hons)